

Paints and varnishes — Pull-off test

The European Standard EN 24624:1992 has the status of a
British Standard

UDC 667.613:620.179.4:620.172

Cooperating organizations

The European Committee for Standardization (CEN), under whose supervision this European Standard was prepared, comprises the national standards organizations of the following countries:

Austria	Oesterreichisches Normungsinstitut
Belgium	Institut belge de normalisation
Denmark	Dansk Standardiseringsraad
Finland	Suomen Standardisoimisliitto, r.y.
France	Association française de normalisation
Germany	Deutsches Institut für Normung e.V.
Greece	Hellenic Organization for Standardization
Iceland	Technological Institute of Iceland
Ireland	National Standards Authority of Ireland
Italy	Ente Nazionale Italiano di Unificazione
Luxembourg	Inspection du Travail et des Mines
Netherlands	Nederlands Normalisatie-instituut
Norway	Norges Standardiseringsforbund
Portugal	Instituto Português da Qualidade
Spain	Asociación Española de Normalización y Certificación
Sweden	Standardiseringskommissionen i Sverige
Switzerland	Association suisse de normalisation
United Kingdom	British Standards Institution

This British Standard, having been prepared under the direction of the Pigment, Paints and Varnishes Standards Policy Committee, was published under the authority of the Standards Board and comes into effect on 15 January 1993

© BSI 12-1998

The following BSI references relate to the work on this standard:
Committee reference PVC/10
Announced in *BSI News*
September 1991

ISBN 0 580 21465 6

Amendments issued since publication

Amd. No.	Date	Comments

Contents

	Page
Cooperating organizations	Inside front cover
National foreword	ii
<hr/>	
Foreword	2
Text of EN 24624	3
<hr/>	
National annex NA (informative) Committees responsible	Inside back cover
National annex NB (informative) Cross-references	Inside back cover

National foreword

This British Standard has been prepared under the direction of the Pigment, Paints and Varnishes Standards Policy Committee. It is identical with ISO 4624:1978 *Paints and varnishes — Pull-off test for adhesion*, published by the International Organization for Standardization (ISO). It supersedes BS 3900-E10:1979, which is withdrawn.

In 1992 the European Committee for Standardization (CEN) accepted ISO 4624:1978 as European Standard EN 24624:1992. As a consequence of implementing the European Standard BS 3900-E10 is renumbered as BS EN 24624:1993. This edition makes no technical changes to the standard.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN title page, pages 2 to 10, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

UDC 667.613:620.179.4:620.172

Descriptors: Paints, varnishes, tests, tension tests, test equipment

English version

Paints and varnishes — Pull-off test

(ISO 4624:1978)

Peintures et vernis — Essai de traction
(ISO 4624:1978)

Lacke und Anstrichstoffe — Abreißversuch
für Haftfähigkeit
(ISO 4624:1978)

This European Standard was approved by CEN on 1992-07-15. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Foreword

This European Standard is the endorsement of ISO 4624. Endorsement of ISO 4624 was recommended by CEN/Technical Committee "Paints and varnishes" under whose competence this European Standard will henceforth fall.

National standards identical to this European Standard will be published at the latest by 93-01-31 and conflicting national standards shall be withdrawn at the latest by 93-01-31.

The standard was approved and in accordance with the CEN/CENELEC Internal Regulations, the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

Contents

	Page
Foreword	
0 Introduction	3
1 Scope and field of application	3
2 Reference	3
3 Apparatus	3
4 Adhesive	5
5 Sampling	6
6 Test substrates	6
7 Procedure	8
8 Notes on procedure	9
9 Expression of results	9
10 Test report	9
Figure 1 — Example of a suitable test apparatus for methods specified in 7.3.1 and 7.3.3	4
Figure 2 — Example of a suitable test apparatus for method specified in 7.3.2	5
Figure 3 — Example of suitable centring device for 20mm diameter test cylinder	7
Figure 4 — Test assembly, sandwich method (substance painted on one or both sides)	8
Figure 5 — Test assembly for rigid substrates	8
Figure 6 — Test assembly using test cylinders	8

0 Introduction

This International Standard is one of a series of standards dealing with the sampling and testing of paints, varnishes and related products. It should be read in conjunction with ISO 1512, ISO 1513, ISO 1514 and ISO 2808.

This International Standard specifies a method for assessing the adhesion of a single coating or a multi-coat system of paint, varnish or related product by measuring the minimum tensile stress necessary to detach or to rupture the coating in a direction perpendicular to the substrate.

The test result is influenced not only by the mechanical properties of the system under test, but also by the nature and preparation of the substrate, the method of paint application, the drying conditions of the coating, temperature, humidity and other factors.

The method of test specified below requires to be completed, for any particular application, by the following supplementary information. This information should be derived from the national standard or other document for the product under test or, if appropriate, shall be the subject of agreement between the interested parties.

- a) Material and surface preparation of test assembly surface or substrate.
- b) Method of application of test coating to the substrate or test cylinder, if appropriate.
- c) Duration and conditions of drying of the coating (or conditions of stoving and ageing, if applicable) before testing.
- d) Thickness, in micrometres, of the dry coating, including the method of measurement in accordance with ISO 2808, and whether it is a single coating or a multi-coat system.
- e) The adhesive (and mixing ratios, if applicable) and curing conditions (see also clause 4).
- f) Duration and conditions between assembly and testing.
- g) Type of pull-off test assembly used (see 7.3).
- h) Type of tensile tester and diameter of test cylinder.

1 Scope and field of application

This International Standard specifies methods for carrying out a pull-off test on a single coating or a multi-coat system of paint, varnish or related product.

The test may be applied using a wide range of substrates. Different procedures are specified according to whether the substrate is deformable, for example thin metal, plastics and wood, or rigid, for example thick concrete and metal plates. For special purposes, the coating may be applied to a test cylinder and, in this case, a method for determination of the coating thickness shall be agreed between the interested parties.

The test result is the minimum tensile stress necessary to break the weakest interface (adhesive failure) or the weakest component (cohesive failure) of the test assembly. Mixed adhesive/cohesive failures may also occur.

2 References

ISO 1512, *Paints and varnishes — Sampling.*

ISO 1513, *Paints and varnishes — Examination and preparation of samples for testing.*

ISO 1514, *Paints and varnishes — Standard panels for testing.*

ISO 2808, *Paints and varnishes — Determination of film thickness.*

3 Apparatus

3.1 Tensile tester, suitable for carrying out the chosen procedure specified in clause 7. The tensile stress shall be applied in a direction perpendicular to the plane of the coated substrate and shall be increased at a substantially uniform rate, not greater than 1 MPa/s¹⁾, such that failure of the test assembly occurs within 90 s. Suitable designs for applying the tensile stress are shown in Figure 1 and Figure 2.

3.2 Test cylinders, suitable for use with the tensile tester (3.1), steel faced, of diameter 20 mm (unless otherwise agreed) and of sufficient thickness to ensure freedom from distortion during the test. It is recommended that the length of the test cylinder should be not less than half its diameter. The faces shall be machined perpendicular to the long axis of the cylinder before use.

¹⁾ 1 MPa/s = 1 MN/m²s

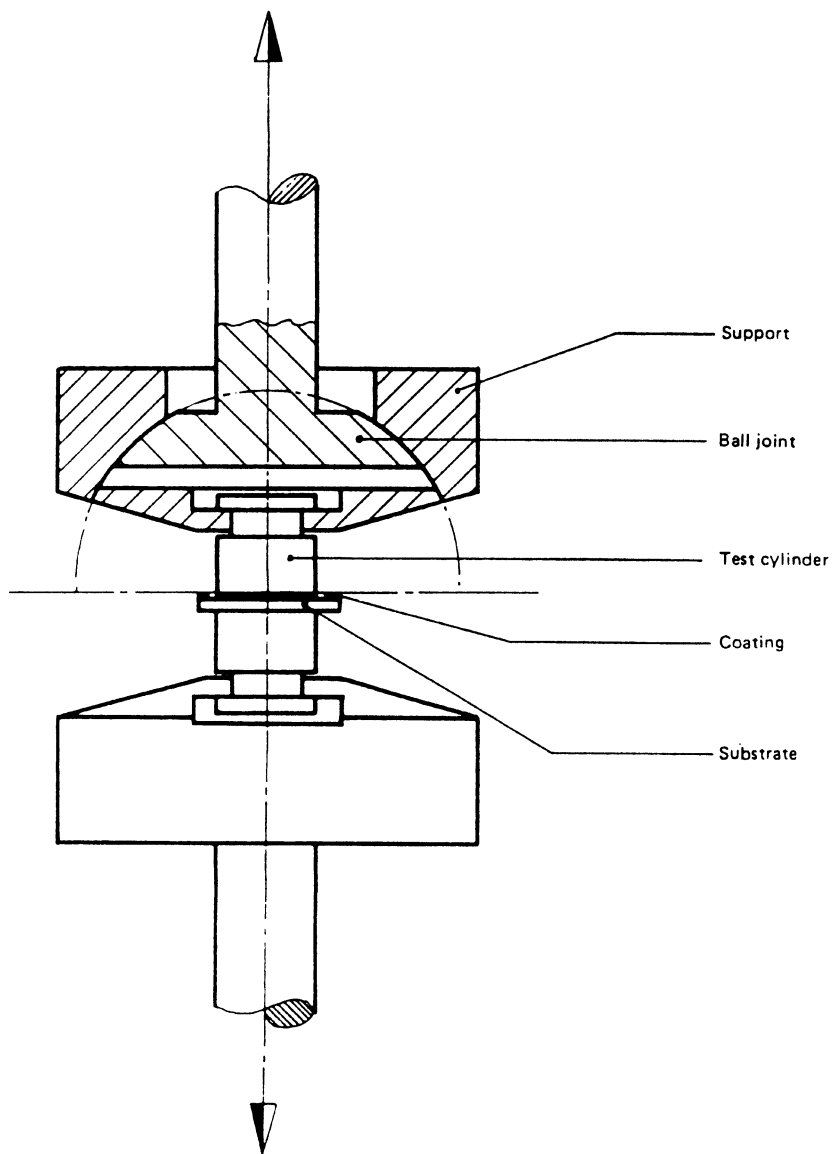


Figure 1 — Example of a suitable test apparatus for methods specified in 7.3.1 and 7.3.3

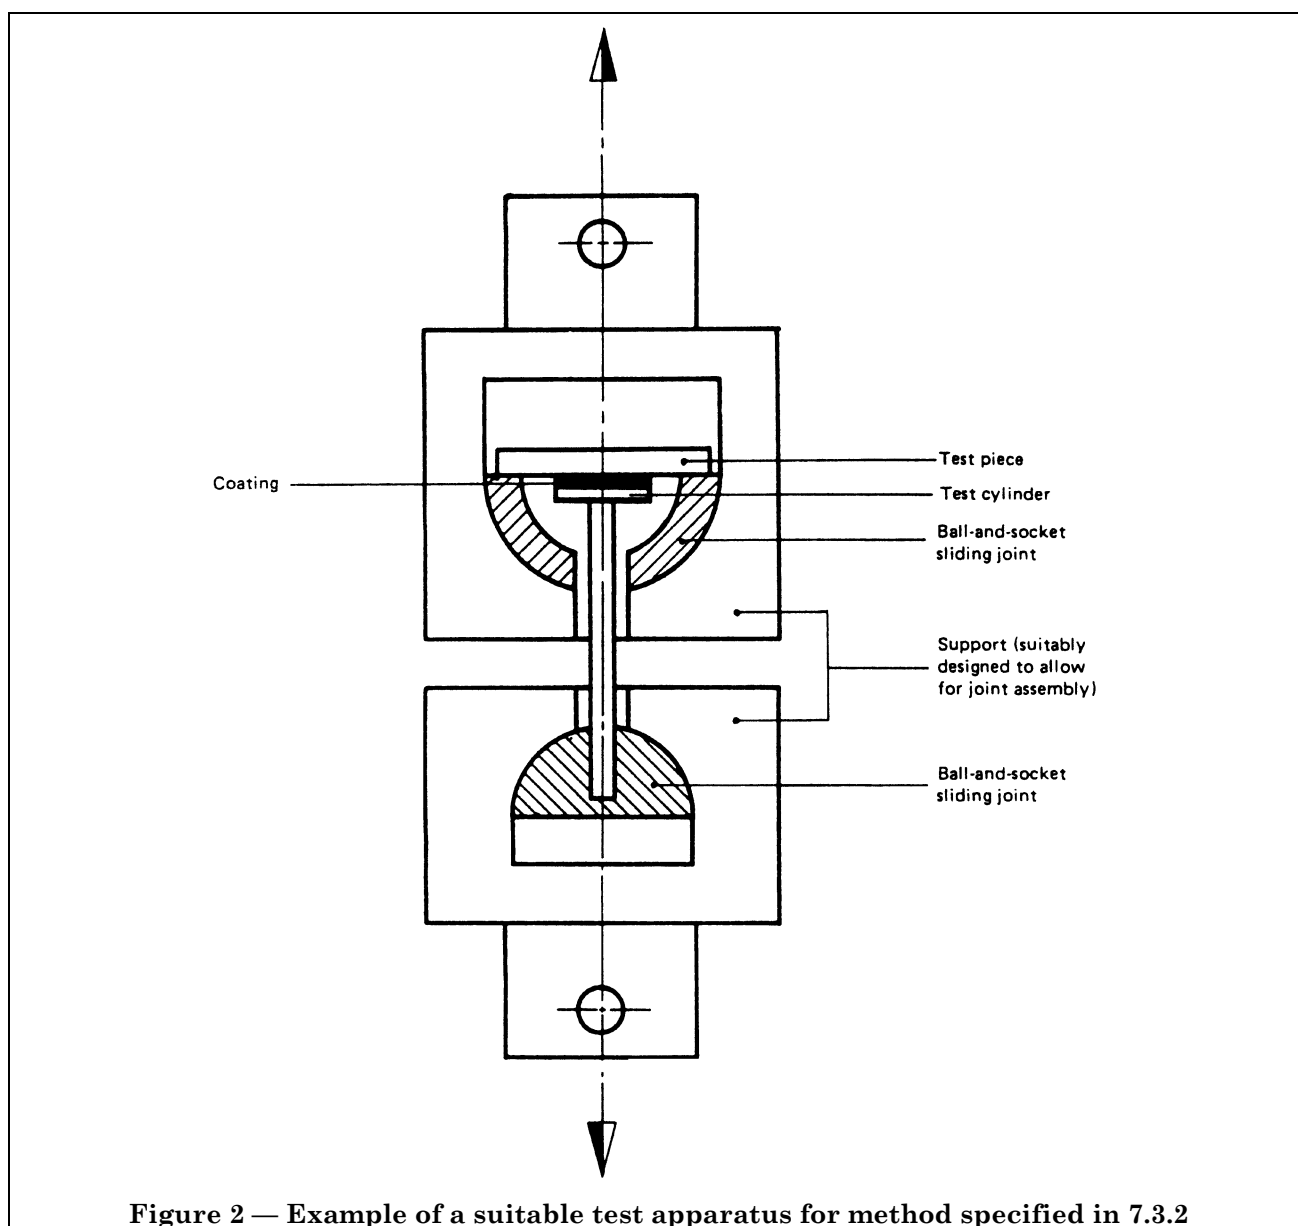


Figure 2 — Example of a suitable test apparatus for method specified in 7.3.2

3.3 Centring device, for ensuring proper coaxial alignment of the test assembly during the adhesion process used as described in 7.3.1 and 7.3.3. A suitable design is shown in Figure 3.

3.4 Cutting device, such as a sharp knife, for cutting through cured adhesive and the paint coating to the substrate, round the circumference of the test cylinder.

4 Adhesives

Special attention is required in selecting suitable adhesives to be used in the test.

To produce failure of the coating, it is essential that the cohesive and bonding properties of the adhesive be greater than those of the coating under test.

Preliminary screening of adhesives shall be carried out in order to determine their suitability for use. Suitable adhesives and, if applicable, their unmixed components shall cause little or no visible change in the coating under test when left in contact with the coating for a period equivalent to the curing time of the adhesive.

An adhesive may be considered suitable for a particular coating if it gives the same test result as that produced by using a different class or type of adhesive when similarly tested.

NOTE In most cases, cyanoacrylate, two-component solventless epoxide and peroxide-catalysed polyester adhesives have been found suitable. Cyanoacrylate and polyester adhesives have a short curing time and are preferred for use with coatings that have been subjected to highly humid conditions.

5 Sampling

Take a representative sample of the product to be tested (or of each product in the case of a multi-coat system) as specified in ISO 1512. Then examine and prepare the sample for testing as specified in ISO 1513.

6 Test substrates

6.1 Preparation and coating of test substrate

Prepare the specified test substrate in accordance with ISO 1514 and then coat it by the specified method with the product or system under test.

6.2 Drying the test coating

Dry (or stove and age) the coated test substrate for the specified time and under the specified conditions and condition it at 23 ± 2 °C and (50 ± 5) % relative humidity for a minimum of 24 h. Then carry out the appropriate test procedure as soon as possible.

6.3 Thickness of coating

Determine the thickness, in micrometres, of the dry coating by one of the procedures specified in ISO 2808. See also clause 1.

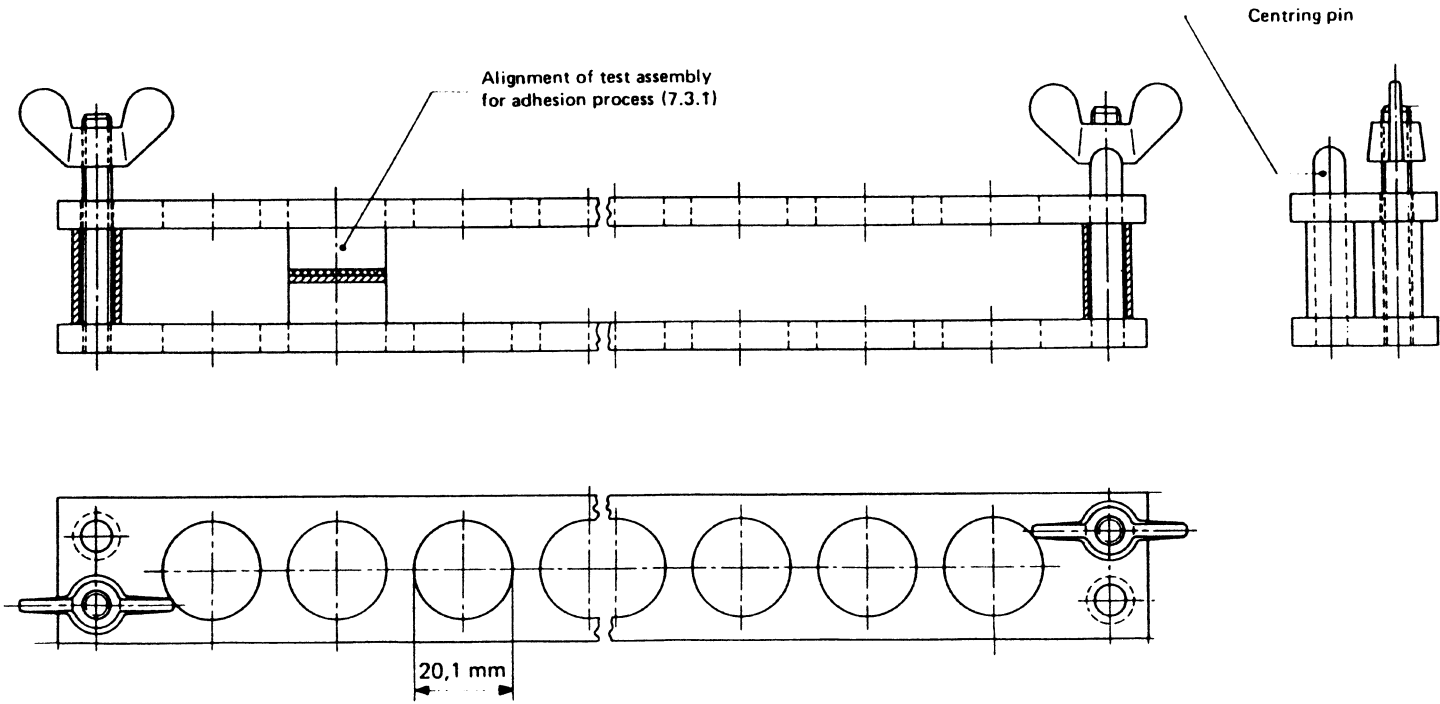


Figure 3 — Example of suitable centring device for 20 mm diameter test cylinders

7 Procedure

7.1 Ambient conditions

Carry out the test at 23 ± 2 °C and (50 ± 5) % relative humidity.


7.2 Adhesives

Prepare and apply the adhesive in accordance with the manufacturer's instructions. Use the minimum quantity of adhesive required to produce a firm, continuous and even bond between the components of the test assembly. Remove any excess adhesive immediately if possible.

7.3 Test assemblies

7.3.1 General method for testing both rigid and deformable substrates

Use as the test piece an area, cut from the coated substrate (disc of minimum diameter 30 mm or square of minimum side 30 mm). Take care not to distort the test piece. Apply the adhesive evenly to the surfaces of two freshly-cleaned test cylinders (3.2) of equal diameter (see notes 1 and 3). Place the test piece between the adhesive-coated faces of the test cylinders such that the test cylinders are coaxially aligned in the centre of the piece, as shown in Figure 4. Align the test assembly in the centring device (3.3) and maintain the alignment for a period equal to the curing time of the adhesive (see note 2). At the end of this period, carefully use the cutting device (3.4) to cut around the circumference of the test cylinders through to the substrate.

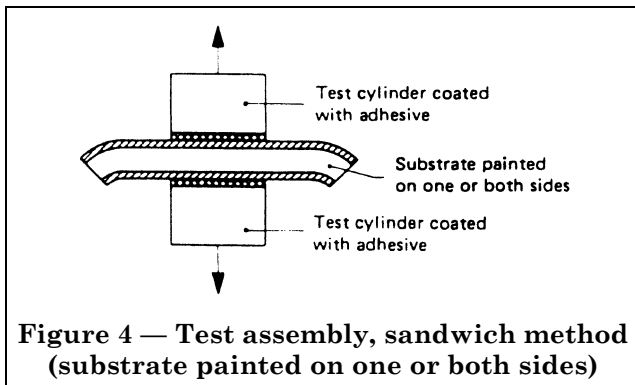


- NOTE 1 The adhesion at the adhesive coating interface may be improved by lightly abrading the surface of the dried coating before application of the adhesive-coated face of the test cylinder.
- NOTE 2 In special tests under highly humid conditions, the curing time of the adhesive shall be as short as possible.
- NOTE 3 In the method for deformable substrates, if a poor adhesive bond is expected between the uncoated face of the substrate and the test cylinder, coat both faces of the substrate with the product under test.

7.3.2 Method for testing from one side only (suitable for rigid substrates only)


Apply the adhesive evenly to the uncoated, freshly-cleaned surface of a test cylinder (3.2). Place the adhesive-coated face of the test cylinder in contact with the coating, (see note 1 in 7.3.1), for a period equal to the curing time of the adhesive (see note 2 in 7.3.1). At the end of this period, carefully use the cutting device (3.4) to cut around the circumference of the test cylinder through to the substrate.

Place the outer ring in position and test as indicated in Figure 5.

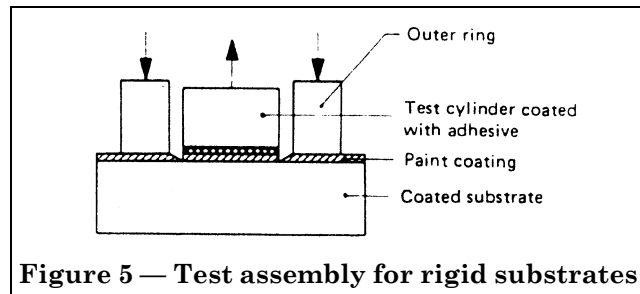

7.3.3 Method using test cylinders

Apply the adhesive evenly to the uncoated, freshly-cleaned surface of a test cylinder. Place the adhesive-coated surface of the test cylinder in contact with the surface of the cylinder coated with the product under test, as shown in Figure 6, and align the test assembly in the centring device (3.3) for a period equal to the curing time of the adhesive.

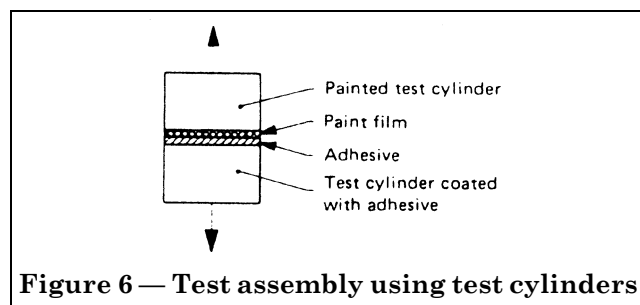

7.4 Measurement

Immediately after the period allowed for the curing of the adhesive, place the test assembly in the tensile tester (3.1), taking care to align the test cylinders so that the tensile force is applied uniformly across the test area, without bending moment. Apply a tensile stress, increasing at a rate not greater than 1 MPa/s, perpendicular to the plane of the coated substrate such that failure of the test assembly shall occur within 90 s of initial application of the stress.

Record the tensile stress to break the test assembly and examine the fracture surfaces in accordance with 9.2.

7.5 Number of determinations

Carry out at least three determinations. For referee purposes, carry out a minimum of five determinations. Report the results of all determinations.

8 Notes on procedure

8.1 The results may be influenced by the test assembly used. Furthermore, the results are not reproducible unless coaxial alignment of the tensile forces is ensured.

8.2 Where failure is mainly associated with the adhesives, the use of another type of adhesive may enable more useful results to be obtained.

9 Expression of results

9.1 Breaking strength

The breaking strength, in megapascals, for each test assembly is given by the formula

$$\frac{4F}{\pi d^2}$$

where

F is the breaking force, in newtons;

d is the diameter, in millimetres, of the test cylinder.

In the case of test cylinders of diameter 20 mm, the breaking strength, in megapascals, is given by the formula

$$\frac{4F}{400\pi} = \frac{F}{314}$$

9.2 Nature of failure

Express the result as the percentage area and site of fracture in the system under test in terms of adhesive, cohesive or adhesive/cohesive failure.

For convenience, the following scheme may be used to describe the results observed.

A = Cohesive failure of substrate

A/B = Adhesive failure between substrate and first coat

B = Cohesive failure of first coat

B/C = Adhesive failure between first and second coats

-/Y = Adhesive failure between final coat and adhesive

Y = Cohesive failure of adhesive

Y/Z = Adhesive failure between adhesive and test cylinder

Example: If a paint system tested in the pull-off test breaks at a tensile stress of 20 MPa and examination of the area on each side of the site of separation reveals approximately 30 % of the test cylinder area associated with cohesive break of the first coat and 70 % of the test cylinder area associated with intercoat adhesive break between the first and second coats, the pull-off test result is expressed as

20 MPa, 30 % B, 70 % B/C

10 Test report

The test report shall contain at least the following information:

- a) the type and identification of the product(s) tested;
- b) a reference to this International Standard or to a corresponding national standard;
- c) the items of supplementary information referred to in the Introduction to this International Standard;
- d) a reference to the national standard or other document supplying the information referred to in c) above;
- e) the result of the test, reported as required in 9.1 and 9.2 (together with any further details required by the document referred to in c) above);
- f) any deviation, by agreement or otherwise, from the procedure specified;
- g) the date of the test.

National annex NA (informative)

Committees responsible

The United Kingdom participation in the preparation of this European Standard was entrusted by the Pigment, Paints and Varnishes Standards Policy Committee (PVC/-) to Technical Committee PVC/10, upon which the following bodies were represented:

British Gas plc
Chemical Industries' Association
Health and Safety Executive
Institute of Metal Finishing
Ministry of Defence
Oil and Colour Chemists' Association
Paint Research Association
Paintmakers' Association of Great Britain Ltd.
Titanium Pigment Manufacturers' Technical Committee

National annex NB (informative)

Cross-references

Publication referred to	Corresponding British Standard
	BS 3900 <i>Methods of test for paints</i>
ISO 1512:1991	Group A <i>Tests on liquid paints (excluding chemical tests)</i> Part A1:1992 <i>Sampling</i>
ISO 1513:1980	Part A2:1983 <i>Examination and preparation of samples for testing</i>
ISO 1514:1984	BS EN 605:1992 <i>Paints and varnishes. Standard panels for testing</i>
ISO 2808:1991	BS 3900 <i>Methods of test for paints</i> Group C <i>Tests associated with paint film formation</i> Part C5:1992 <i>Determination of film thickness</i>

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.