

Flexible sheets for waterproofing — Bitumen sheets for roof waterproofing — Determination of flexibility at low temperature

The European Standard EN 1109:1999 has the status of a
British Standard

ICS 91.100.50

National foreword

This British Standard is the official English language version of EN 1109:1999.

The UK participation in its preparation was entrusted to Technical Committee B/546 Flexible sheets for waterproofing, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled "International Standards Correspondence Index", or by using the "Find" facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 7 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard, having been prepared under the direction of the Building and Civil Engineering Sector Committee, was published under the authority of the Standards Committee and comes into effect on 15 February 2000

BSI 02-2000

ISBN 0 580 35734 1

Amendments issued since publication

Amd. No.	Date	Comments

ICS 91.100.50

English version

Flexible sheets for waterproofing - Bitumen sheets for roof waterproofing - Determination of flexibility at low temperature

Feuilles souples d'étanchéité - Feuilles d'étanchéité de toiture bitumineuses - Détermination de la souplesse à basse température

Abdichtungsbahnen - Bitumenbahnen für Dachabdichtungen - Bestimmung des Kaltbiegeverhaltens

This European Standard was approved by CEN on 11 July 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Contents

	Page
Foreword.....	3
Introduction	3
1 Scope	3
2 Normative references	3
3 Definitions	4
4 Principle	4
5 Apparatus	4
6 Sampling	5
7 Preparation of test specimens	6
8 Procedure	6
8.1 Preparation of apparatus	6
8.2 Conditioning of test specimens	6
8.3 Flexibility at a specified temperature	6
8.4 Determination of cold bending temperature	6
9 Recording of results, evaluation and precision of test method	7
10 Test report	7

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 254, Flexible sheets for waterproofing, the Secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by February 2000, and conflicting national standards shall be withdrawn at the latest by September 2001.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Introduction

This European Standard is intended for the characterization and/or classification of bitumen sheets as manufactured or supplied before use. The test method relates exclusively to products, or to their components where appropriate, and not to waterproofing membrane systems composed of such products and installed in the works.

This test is intended to be used in conjunction with European Standards on product specification for reinforced and unreinforced bitumen sheets for roofing.

The test for flexibility at a low temperature is intended to determine the susceptibility to cracking of the bituminous coating on a sheet when bent under specified conditions. The test result is dependent on the type of coating, on the thickness of the sheet, type and position of the reinforcement and the behaviour of the surfacing material. The use of the test results directly to compare the performance of coatings in sheets of different composition is strictly limited because of the influence of parameters which have not been quantified. Only the results from sheets with the same composition can be used to compare the performance of the coating directly.

The test primarily serves to characterize bitumen sheets. It can also be used to evaluate the change in the cold bending behaviour during artificial ageing. It is not safe to relate the test results to the actual performance to be expected at low temperatures in service.

1 Scope

This European Standard specifies the determination of flexibility of reinforced bitumen sheets at low temperatures. Sheets without reinforcement can also be tested using this standard.

The test is carried out on the upper and lower faces of the sheet either at a predetermined temperature or successively at different temperature steps to determine the cold bending temperature which represents a limiting temperature. Therefore the test can be used to confirm a minimum cold bending temperature for a product or to determine the specific cold bending temperature for the product, e.g. to determine the change of these properties as a result of artificial ageing.

2 Normative references

This European Standard incorporates by dated or undated references provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references, the latest edition of the publication referred to applies.

ISO 5725:1986 Precision of test methods - Determination of repeatability and reproducibility for a standard test method by inter-laboratory tests.

3 Definitions

For the purposes of this standard the definitions indicated in 3.1 to 3.3 and in the corresponding European Standards on product specifications apply.

3.1 flexibility the ability of bitumen sheet test specimens to be bent under specified conditions without cracking

3.2 cold bending temperature the lowest temperature at which bitumen sheet test specimens can be bent around a specified mandrel without cracking

3.3 crack a fissure in the coating of the bitumen sheet extending to the reinforcement or completely through unreinforced sheets

4 Principle

The test specimens taken from the test sample are bent at the upper side or under side respectively through an angle of 180 ° in a mechanical bending apparatus immersed in a coolant. After bending, the test specimens are examined for the presence of cracks in the coating.

5 Apparatus

The construction and method of operation of the apparatus are shown in Figure 1. The apparatus consists of two non-rotating cylinders ($20 \pm 0,1$) mm in diameter and a cylindrical or semi-cylindrical bending mandrel ($30 \pm 0,1$) mm in diameter, capable of moving upwards, placed between them. The distance *a* between the cylinders is adjustable so that the distance between the cylinders and the bending mandrel can be adjusted to the thickness of the sheet.

The whole apparatus is immersed in a thermostatic bath which can be controlled between +20 °C and -40 °C to the nearest 0,5 °C. The coolant used shall be either a mixture of

- monopropylene glycol solution¹⁾/water (volume ratio 1:1) down to -25 °C or
- below -20 °C a mixture of ethanol/water (volume ratio 2:1).


To check the test temperature, an additional thermometer capable of measuring to 0,5 °C is required; its thermosensor shall be placed in the test medium at the same level as the test specimen.

To position the test specimens in the test liquid so that they are flat and completely immersed for conditioning, suitable removable holding devices shall be used. The holding devices should be capable of taking at least the five test specimens in a series.


For the test, the bending mandrel is raised from below against the test specimen at a speed of 360 mm/min so that the test specimen is bent through an angle of 180° and the electronic control system shall ensure that the travel speed is maintained at (360 ± 40) mm/min at each phase of the bending process and at each temperature. Cracks are detected by visual inspection without any additional aids by the person carrying out the test. To permit an accurate assessment, the travel path is defined in such a way that the test specimen projects out of the coolant at the end of the procedure. The travel section shall be limited by suitably set limit switches.

¹⁾ Monopropylene glycol = 1,2 propanediol (IUPAC).

Dimensions in millimetres

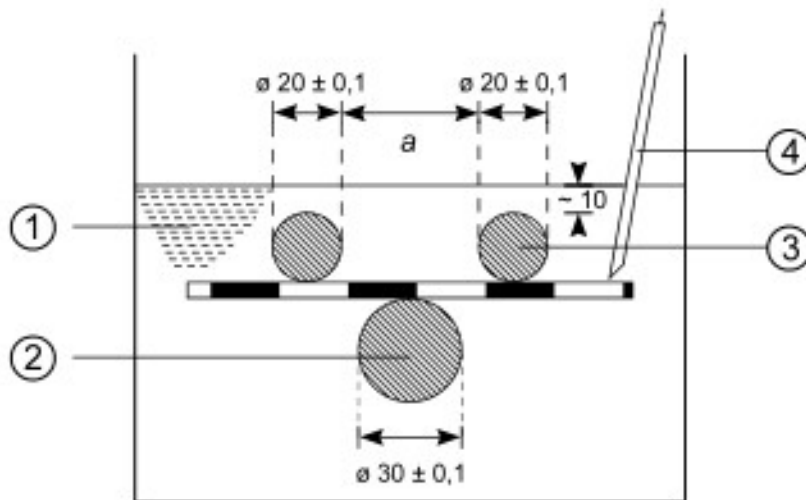

1a) Beginning of bending

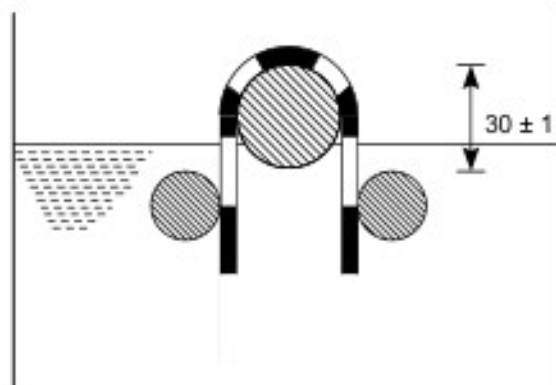

1b) End of bending

Legend: (1) coolant (2) bending mandrel (3) fixed cylinder (4) thermosensor

Figure 1: Principle of test apparatus and bending process

6 Sampling

Test samples shall be taken in accordance with the corresponding European Standard.

Rectangular test specimens with dimensions of (140 ± 1) mm x (50 ± 1) mm as required by the tests described in 8.3 or 8.4 are taken from the test sample uniformly over the width of the sheet and with the larger dimension in the longitudinal direction of the sheet. The test specimens shall not be taken within approximately 150 mm of the edges of the sheet. The test specimens shall be numbered consecutively, beginning from one edge of the sheet, and the upper and lower faces of the sheet shall be marked.

7 Preparation of test specimens

Any protective film shall be removed, preferably by applying a strip of adhesive tape to it at ambient temperature, cooling the test specimen to approximately the presumed cold bending temperature and then pulling the adhesive tape from the test specimen. Alternatively or additionally, the film can be removed by means of a compressed air jet (maximum pressure approximately 5 bar, nozzle diameter approximately 0,5 mm). If it is not possible to remove the film using these methods, a gas flame may be used but for the least time necessary to destroy the film but not to otherwise damage the test specimen.

The test specimens shall then be conditioned prior to the test for at least 4 h at (23 ± 2) °C on a flat support so that they do not touch each other and there can be no adhesive connection with the support. Where necessary a sheet of siliconized paper can be used for this. Loose surface granules shall be removed before by hand by gentle tapping.

8 Procedure

8.1 Preparation of apparatus

Prior to beginning the series of tests, the distance *a* (see Figure 1) between the cylinders shall be adjusted to the thickness of the test specimen so that it is approximately 32 mm plus twice the thickness of the test specimen. The apparatus is then placed in the refrigerant bath so that the top of the cylinders is approximately 10 mm beneath the surface of the coolant. The bending mandrel is then in the bottom position.

8.2 Conditioning of test specimens

After the specified test temperature in the coolant has been reached to the nearest 0,5 °C, the test specimens are inserted into the holding device at the height of the cylinders so that coolant freely circulates around them. The test specimens are conditioned for $1 \text{ h} \pm 5 \text{ min}$ in the coolant from the time when the temperature of the coolant is restored. The thermosensor positioned approximately level with the test specimens is used for checking the temperature of the coolant. Then, the test specimens are tested as described in 8.3 or 8.4.

8.3 Flexibility at a specified temperature

Two series of five test specimens are conditioned as described in 8.2 at the specified test temperature, which is intended to be a whole number. One series are for testing the upper face of the sheet and the other for the lower face. Then they are tested as follows.

The test specimens are placed successively between the bending mandrel and cylinders with the face to be tested uppermost. The bending mandrel is then set in motion pushing upwards against the test specimens at a speed of (360 ± 40) mm/min so that the test specimens are bent uniformly around it. The travel shall stop (30 ± 1) mm above the cylinders (see Figure 1). The surface of the test specimens shall be projecting clearly out of the coolant; otherwise the fluid level shall be lowered accordingly.

Within 10 s after the completion of the bending procedure the test specimen is examined under a suitable light source for any cracks using the naked eye and, if necessary, with additional optical aids. A crack exists if one or more fissures in the coating extend to the reinforcement or completely through unreinforced sheets. All five test specimens in a series are tested immediately after each other. If the dimensions of the apparatus are adequate, simultaneous testing of several test specimens is possible.

8.4 Determination of cold bending temperature

If the cold bending temperature of a bitumen sheet is to be determined (e.g. to show changes resulting from artificial ageing), then the following procedure shall be carried out using the test described in 8.3:

The range of the (unknown) cold bending temperature shall be determined initially by tests on individual test specimens in steps of 6 °C, starting at the expected cold bending temperature. The test temperatures in each case therefore are always in multiples of 6 °C (e.g. -12 °C, -18 °C, -24 °C etc.). Therefore starting with the maximum temperature step leading to breakage, there follows a closer determination into 2 °C steps on series of five test specimens for the upper face and lower face of the sheet. This step-by-step change of the test temperature by 2 °C each time shall be continued until at least four of the five test specimens tested immediately after each other in one series has no crack. This temperature step is designated as the cold bending temperature and represents the result of the test.

9 Recording of results, evaluation and precision of test method

9.1 Result of flexibility at a specified temperature

The test described in 8.3 is passed if at least four of the five test specimens have no crack on the tested face of the sheet at the specified temperature. The results of the tests of the upper face and lower face shall be indicated separately.

9.2 Results when determining cold bending temperature

When determining the cold bending temperature, if at least four of the five test specimens have successfully passed the test as described in 8.4 at one temperature step, this is the cold bending temperature for the face of the sheet tested. The results of the tests of the upper face and lower face shall be indicated separately. (The upper and lower faces of the bitumen sheet can have different cold bending temperatures.)

9.3 Precision of the measuring method

The precision values were determined by an initial international inter-laboratory test in following ISO 5725:1986; they relate only to sheets with reinforcement and polymer-modified coatings.

9.3.1 Repeatability

- | | |
|---|-----------------------------|
| - repeatability standard deviation of results: | $\sigma_r = 1,2 \text{ °C}$ |
| - confidence interval (95%) of a result: | $q_r = 2,3 \text{ °C}$ |
| - repeatability limit (difference between two results): | $r = 3 \text{ °C}$ |

9.3.2 Reproducibility

- | | |
|--|-----------------------------|
| - reproducibility standard deviation of results: | $\sigma_R = 2,2 \text{ °C}$ |
| - confidence interval (95%) of a result: | $q_R = 4,4 \text{ °C}$ |
| - reproducibility limit (different between two results): | $R = 6 \text{ °C}$ |

10 Test report

The test report shall include at least the following information:

- all details necessary to identify the product tested;
- a reference to this standard (EN 1109), and any deviation from it;
- information on sampling in accordance with clause 6;
- details of preparation of the test specimens in accordance with clause 7;
- the test results in accordance with 9.1 or 9.2;
- the date of the test.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.